

Information about the content

Scope:	Plansee SE	Prepared/Updated:	Joachim RESCH
		Released:	Wolfgang GLATZ
Valid from:	03-May-2021	Controlled:	PSE-020

This document is subject to electronic version control – confirm revision status before using.

This specification covers recrystallized sheets made of lanthanum oxide doped molybdenum.

1 Dimensions and tolerances

1.1 Thickness- and width tolerances

Sheet thickness	Thickness tolerances	Max. width	Width tolerances
[mm]	[± mm or % of the thickness]	[mm]	[mm]
1,00	± 0,08	850	± 2,0
> 1,00 – ≤ 1,50	± 0,13	850	± 2,0
> 1,50 – ≤ 2,00	± 0,15	850	± 2,0
> 2,00 – ≤ 3,60	± 0,18	1000	± 2,0
> 3,60 – 50,00	± 5 %	1000	± 2,0

1.2 Length tolerance

The length tolerance for sheet length up to 2500 mm is max. + 5 / - 0 mm.

The maximum sheet dimensions depend on the sheet thickness. Other dimensions upon request.




Details to our certificates
at www.plansee.com



1.3 Flatness

Flatness: max. 4 % (measuring procedure on the basis of ASTM B386)

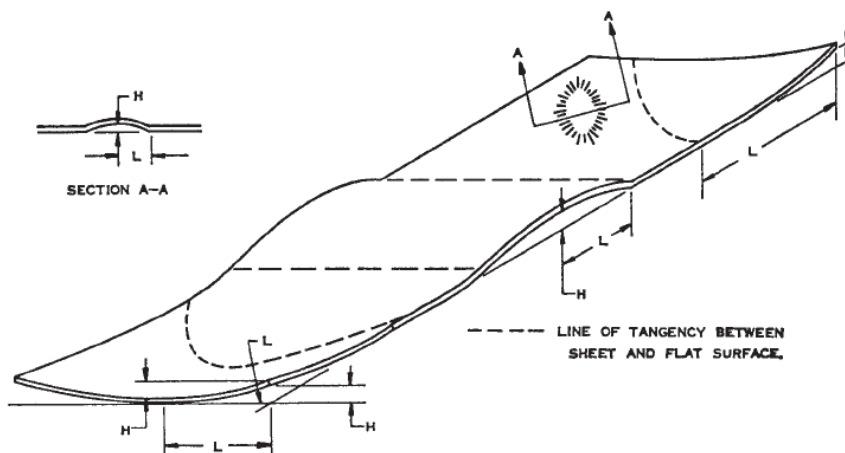

Flatness Deviation, % = $(H/L) \times 100$

H = maximum distance between flat surface and lower surface of sheet.

L = minimum distance between highest point on sheet and point of contact with flat surface.



Details to our certificates
at www.plansee.com



1.4 Sheet cuts

These cuts are being produced from the sheets described in (1.1).

a) Tolerances for sheet cuts:

Thickness \leq 15 mm: DIN-ISO 2768 Part 1 Tolerance class m (medium)
Thickness $>$ 15 mm: DIN-ISO 2768 Part 1 Tolerance class c (coarse)

b) Flatness:

The same specified limits as defined for sheets (see 1.3) apply for the sheet cuts.

c) Proportion of length to width:

The length and/or the width must in any case exceed the thickness, maximal width 1000 mm.

Length [mm]	Minimal width [mm]
20 - 400	20
$>$ 400 - 1000	40
$>$ 1000 - 2500	60

d) Discs and Rings:

Stated below, minimal ring width, minimal hole diameter 3 mm.

Diameter* [mm]	Minimal width for rings [mm]
\geq 15 - 50	4
$>$ 50 - 100	10
$>$ 100 - 500	15
$>$ 500 - 1000	20

* Diameter for discs, external diameter for rings

Other dimensions on request.



Details to our certificates
at www.plansee.com



2 Physical and mechanical product properties

Density:	$\geq 10,1 \text{ g/cm}^3$
Hardness Vickers: ^{a)}	$\leq 250 \text{ HV}$

a) The actual value quoted in certificates corresponds to the mean-value of a representative control sample.

Remarks: All MLR sheets are delivered recrystallized ($\geq 90 \%$ recrystallized in micrograph).

2.1 Surface condition

Appearance:	The material will be of uniform quality, free from foreign matter, splits and fractures. Bed sheets (not trimmed) may have small edge cracks. Surface defects are assessed in the frame of visual inspection. Local surface defects can be removed by grinding within the specified thickness tolerance.
Surface quality:	Pickled (dull)



Details to our certificates
at www.plansee.com



3 Chemical composition

Main and minor components	Plansee		EU-Directive
	Content [%]		RoHS ^{a)}
Mo	Balance ^{b)}		-
La	0,52 - 0,62		-
La ₂ O ₃	0,61 - 0,73		-
Impurities	Max. values [µg/g]		Max. values [µg/g]
	Typical	Guaranteed	
Al	1	10	-
Cr	3	20	-
Cu	2	20	-
Fe	5	20	-
K	6	20	-
Ni	1	10	-
Si	2	20	-
W	169	300	-
C	13	30	-
H	-	10	-
N	1	10	-
Cd	1	5	100
Hg ^{c)}	-	1	1000
Pb	-	5	1000
Cr (VI)			1000
Organic impurities (e.g. PBB, PBDE, PFOS, PFOA)	- **)	- **)	1000

a) EU-directives 2015/863/EU, 2011/65/EU and 2000/53/EC

b) Metallic Purity without W

b) Initial value

**) The presence of Cr (VI) and organic impurities can definitely be excluded because of the production process (multiple heat treatments at temperatures above 1000 °C in H₂-atmosphere).

The chemical composition is checked by means of random sampling. The sampling inspection plan, analysis and evaluation methods are determined in the internal instruction PSE-020-WI-003. The application of the measured values for the chemical analysis is defined in PSE-680-WI-001.

Remarks: The specified physical and chemical characteristics are disclosed not regarding measurement accuracy.



Details to our certificates
at www.plansee.com



4 Packaging, labelling, storage and certification

4.1 Packaging, labelling and storage

Standard individual packing: depending on their size, the sheets will be either packed individually or in parcels with liner between the different pieces.

Each package will be provided with a label with the following information:

Producer's name:	Plansee
Plansee order number:	
Lot number:	
Material number:	
Material:	MLR
Dimension:	e.g. thickness, width, length, diameter, etc.
Quantity:	Total quantity in kg
Date:	

The material must be kept in a dry place and protected from mechanical damage. It is best to keep the material in the original packing until used.

Special packing: (extra costs will be invoiced)

Special packing should be used if the material is stored under unusual conditions or aggressive atmosphere (e.g. sea air, ...).

4.2 Inspection documents

Following inspection documents will be supplied upon customer request according to EN 10 204:

Test report 2.2

Plansee confirms with this test report that the delivered product meets the specification and gives details of the material properties according to ongoing production surveillance, not directly related to the particular production batch.

Inspection certificate 3.1 (extra costs will be invoiced)

An inspection officer from Plansee confirms with this inspection certificate that the delivered product meets the specification and gives test results related to the particular production batch.



Details to our certificates
at www.plansee.com



5 Order instructions

Please quote following information when ordering:

- Product description
- Quality (the number of this specification must be mentioned)
- Dimension: thickness (width, length, diameter, etc.)
- Quantity (total quantity in kg or in piece)
- Required certificate and content in case of a 3.1 inspection certificate
- *For special packing:* Specification of packaging

For further information on our delivery possibilities, please look into our <http://www.plansee.com>

6 Referenced standards

The standards applied for the test methods are listed in the Plansee standard infobase and are made available upon request.

Changes to last version:

Replacement for PSE-605-PS-026 Rev. 02

- Section 3: Table 2 chemical composition, header "min. content" to "content"



Details to our certificates
at www.plansee.com

